



# University of HUDDERSFIELD

## University of Huddersfield Repository

Morris, Gordon, Castile, J., Smith, A., Adams, G. G. and Harding, S. E.

Macromolecular conformation of chitosan in dilute solution: A new global hydrodynamic approach

### Original Citation

Morris, Gordon, Castile, J., Smith, A., Adams, G. G. and Harding, S. E. (2009) Macromolecular conformation of chitosan in dilute solution: A new global hydrodynamic approach. *Carbohydrate Polymers*, 76 (4). pp. 616-621. ISSN 0144-8617

This version is available at <http://eprints.hud.ac.uk/id/eprint/16239/>

The University Repository is a digital collection of the research output of the University, available on Open Access. Copyright and Moral Rights for the items on this site are retained by the individual author and/or other copyright owners. Users may access full items free of charge; copies of full text items generally can be reproduced, displayed or performed and given to third parties in any format or medium for personal research or study, educational or not-for-profit purposes without prior permission or charge, provided:

- The authors, title and full bibliographic details is credited in any copy;
- A hyperlink and/or URL is included for the original metadata page; and
- The content is not changed in any way.

For more information, including our policy and submission procedure, please contact the Repository Team at: [E.mailbox@hud.ac.uk](mailto:E.mailbox@hud.ac.uk).

<http://eprints.hud.ac.uk/>

# Macromolecular conformation of chitosan in dilute solution: a new global hydrodynamic approach

Gordon A. Morris<sup>a,✉</sup>, Jonathan Castile<sup>b</sup>, Alan Smith<sup>b</sup>, Gary G. Adams<sup>a</sup> and Stephen E. Harding<sup>a</sup>

<sup>a</sup>National Centre for Macromolecular Hydrodynamics, School of Biosciences, University of Nottingham, Sutton Bonington, LE12 5RD, U.K.

<sup>b</sup>Archimedes Development Limited, Albert Einstein Centre, Nottingham Science and Technology Park, University Boulevard, Nottingham, NG7 2TN, U.K.

✉Corresponding author

Tel: +44 (0) 115 9516149

Fax: +44 (0) 115 9516142

Email: [gordon.morris@nottingham.ac.uk](mailto:gordon.morris@nottingham.ac.uk)

## Abstract

Chitosans of different molar masses were prepared by storing freshly prepared samples for up to 6 months at either 4 °C, 25 °C or 40 °C. The weight-average molar masses,  $M_w$  and intrinsic viscosities,  $[\eta]$  were then measured using size exclusion chromatography coupled to multi-angle laser light scattering (SEC-MALLS) and a “rolling ball” viscometer, respectively.

The solution conformation of chitosan was then estimated from:

- (a) the Mark-Houwink-Kuhn-Sakurada (MHKS) power law relationship  $[\eta] = kM_w^a$  and
- (b) the persistence length,  $L_p$  calculated from a new approach based on equivalent radii (Ortega A. and Garcia de la Torre, *J. Biomacromolecules*, 2007, 8, 2464-2475).

Both the MHKS power law exponent ( $a = 0.95 \pm 0.01$ ) and the persistence length ( $L_p = 16 \pm 2$  nm) are consistent with a semi-flexible rod type (or stiff coil) conformation for all 33 chitosans studied. A semi-flexible rod conformation was further supported by the Wales van-Holde ratio, the translational frictional ratio and sedimentation conformation zoning.

**Keywords:** chitosan; intrinsic viscosity; molar mass; sedimentation coefficient; equivalent radii; semi-flexible rod conformation

## Introduction

Due to being in the unique position of being the only “natural” polycationic polymer chitosan and its derivatives have received a great deal of attention from the food, cosmetic and pharmaceutical industries. Important applications include water and waste treatment, antitumor, antibacterial and anticoagulant properties (Rinaudo, 2006). The interaction of chitosan with mucus is also important in oral and nasal drug delivery (Harding, Davis, Deacon, & Fiebrig, 1999).

Chitosan is the generic name for a family of strongly polycationic derivatives of poly-N-acetyl-D-glucosamine (chitin) extracted from the shells of crustaceans or from the mycelli of fungi (Rinaudo, 2006; Tombs, & Harding, 1998). In chitosan (**Figure 1**) the N-acetyl group is replaced either fully or partially by  $\text{NH}_2$  therefore the degree of acetylation can vary from  $\text{DA} = 0$  (fully deacetylated) to  $\text{DA} = 1$  (fully acetylated *i.e.* chitin).

<**Figure 1 here**>

Chitosan is only soluble at acidic pH ( $\text{pH} < 6$ ) and, therefore, the amine groups exist predominantly in the  $\text{NH}_3^+$  form resulting in a highly charged polycationic chain and which is reported to have either a rigid rod-type structure (Terbojevich, Cosani, Conio, Marsano, & Bianchi, 1991; Errington, Harding, Vårum, & Illum, 1993; Cölfen, Berth, & Dautzenberg, , 2001; Fee, Errington, Jumel, Illum, Smith, & Harding, 2003; Kasaai, 2007) or a semi-flexible-coil (Rinaudo, Milas, & Le Dung, 1993; Berth, Dautzenberg, & Peter, 1998; Brugnerotto, Desbrières, Roberts, & Rinaudo, 2001; Schatz, Viton, Delair, Pichot, & Domard, 2003; Mazeau and Rinaudo, 2004; Vold, 2004; Lamarque, Lucas, Viton, & Domard, 2005; Velásquez, Albornoz, & Barrios, 2008).

In this paper we will discuss the conformation of chitosan using a recent advancement in the analysis in the molar mass dependencies of intrinsic viscosity and the sedimentation coefficient (Ortega, & Garcia de la Torre, 2007).

## Materials and Methods

### Samples

Chitosans (x 3) of degree of acetylation (DA) of ~ 20 % were obtained from Pronova Biomedical (Oslo, Norway) and from Sigma Chemical Company (St. Louis, U.S.A.) and were used without any further purification. Chitosans (200 mg) were dissolved in 0.2 M pH 4.3 acetate buffer (100 ml) with stirring for 16 hours. The sedimentation coefficient, weight average molar mass and intrinsic viscosity for each chitosan was measured directly after preparation. Additionally the weight average molar masses and intrinsic viscosities were measured after the storage of the each of the three chitosan samples for 2 weeks at 25 °C and for 1, 3 and 6 months at either 4 °C, 25 °C or 40 °C. Resultant chitosans were numbered 1 to 33 in descending molar mass order.

### Viscometry

The densities and viscosities of samples solutions and reference solvents were analysed using an AMVn Automated Micro Viscometer and DMA 5000 Density Meter (both Anton Paar, Graz, Austria) under precise temperature control ( $20.00 \pm 0.01$  °C). The relative,  $\eta_{rel}$  and specific viscosities,  $\eta_{sp}$  were calculated as follows:

$$\eta_{rel} = \left( \frac{\eta}{\eta_0} \right) \quad (1)$$

$$\eta_{sp} = \eta_{rel} - 1 \quad (2)$$

where  $\eta$  is the dynamic viscosity (*i.e.* corrected for density) of a chitosan solution and  $\eta_0$  is the dynamic viscosity of buffer (1.0299 mPas).

Measurements were made at a single concentration ( $\sim 1.0 \times 10^{-3}$  g ml<sup>-1</sup>) and intrinsic viscosities,  $[\eta]$ , were estimated using the Solomon-Ciutâ approximation (Solomon, & Ciutâ, 1962):

$$[\eta] \approx \frac{\eta_{sp} - 2 \ln \eta_{rel}}{c} \quad (3)$$

### *Size Exclusion Chromatography coupled to Multi-Angle Laser Light Scattering (SEC-MALLS)*

Analytical fractionation was carried out using a series of SEC columns TSK G6000PW, TSK G5000PW and TSK G4000PW protected by a similarly packed guard column (Tosoh Bioscience, Tokyo, Japan) with on-line MALLS (Dawn DSP, Wyatt Technology, Santa Barbara, U.S.A.) and refractive index (Optilab rEX, Wyatt Technology, Santa Barbara, U.S.A.) detectors. The eluent (0.2 M pH 4.3 acetate buffer) was pumped at  $0.8 \text{ ml min}^{-1}$  (PU-1580, Jasco Corporation, Great Dunmow, U.K.) and the injected volume was  $100 \text{ }\mu\text{l}$  ( $\sim 1.0 \times 10^{-3} \text{ g ml}^{-1}$ ) for each sample. Absolute weight-average molar masses ( $M_w$ ) were calculated using the ASTRA<sup>®</sup> (Version 5.1.9.1) software (Wyatt Technology, Santa Barbara, U.S.A.), using the refractive index increment,  $dn/dc = 0.163 \text{ ml g}^{-1}$  (Rinaudo et al., 1993).

### *Sedimentation Velocity in the Analytical Ultracentrifuge*

Sedimentation velocity experiments were performed using a Beckman Instruments (Palo Alto, U.S.A.) Optima XLI Analytical Ultracentrifuge. Chitosan solutions ( $380 \text{ }\mu\text{l}$ ) of various concentrations ( $0.1 - 3.0 \text{ mg/ml}$ ) and  $0.2 \text{ M}$  pH 4.3 acetate buffer ( $400 \text{ }\mu\text{l}$ ) were injected into the solution and reference channels, respectively of a double sector  $12 \text{ mm}$  optical path length cell. Samples were centrifuged at  $45000 \text{ rpm}$  at a temperature of  $20.0 \text{ }^\circ\text{C}$ . Concentration profiles and the movement of the sedimenting boundary in the analytical ultracentrifuge cell were recorded using the Rayleigh interference optical system and converted to concentration (in units of fringe displacement relative to the meniscus,  $j$ ) versus radial position,  $r$  (Harding, 2005). The data was then analysed using the “least squares, ls-g( $s$ ) model” incorporated into the SEDFIT (Version 9.4b) program (Schuck, 1998; Schuck, 2005). This software based on the numerical solutions to the Lamm equation follows the changes in the concentration profiles with radial position and time and generates an apparent distribution of sedimentation coefficients in the form of  $g^*(s)$  versus  $s_{T,b}$ , where the \* indicates that the distribution of sedimentation coefficients has not been corrected for diffusion effects (Harding, 2005).

As sedimentation coefficients are temperature and solvent dependent it is conventional to convert sedimentation coefficients (or their distributions) to the

standard conditions of 20.0 °C and water using the following equation (Ralston, 1993).

$$s_{20,w} = s_{T,b} \left[ \frac{(1 - \bar{v} \rho_{20,w}) \eta_{T,b}}{(1 - \bar{v} \rho_{T,b}) \eta_{20,w}} \right] \quad (4)$$

where  $\bar{v} = 0.57 \text{ ml g}^{-1}$  is the partial specific volume of chitosan (Errington et al., 1993) and  $\eta_{T,b}$  and  $\rho_{T,b}$  are the viscosity and density of the experimental solvent (0.2 M pH 4.3 acetate buffer) at the experimental temperature (20.0 °C) and  $\eta_{20,w}$  and  $\rho_{20,w}$  are the viscosity and density of water at 20.0 °C.

To account for hydrodynamic non-ideality (co-exclusion and backflow effects), the apparent sedimentation coefficients ( $s_{20,w}$ ) were calculated at each concentration and extrapolated to infinite dilution using the following equation (Gralén, 1944; Rowe, 1977; Ralston, 1993).

$$\frac{1}{s_{20,w}} = \frac{1}{s_{20,w}^0} (1 + k_s c) \quad (5)$$

where  $k_s$  ( $\text{ml g}^{-1}$ ) is the sedimentation concentration dependence or “Gralén” coefficient (Gralén, 1944).

## Results and Discussion

### *Intrinsic viscosity and molar mass*

Intrinsic viscosities and weight-average molar masses (**Table 1**) are in the range 270 – 1765 ml g<sup>-1</sup> and 65000 – 425000 g mol<sup>-1</sup>, respectively reflecting depolymerisation of the chitosan chain upon storage at different temperatures for different times.

### *Sedimentation coefficient*

The sedimentation coefficients (Table 2) were calculated for three chitosans (1, 8 and 25) and reflect the differences in molar mass between the samples.

<Tables 1 & 2 here>

### *Conformational analysis*

#### 1. *Mark-Houwink-Kuhn-Sakurada exponent “a”*

Hydrodynamic results obtained from SEC-MALLs and viscosity measurement were further used to study the gross conformation of chitosan (Harding, Vårum, Stokke, & Smidsrød, 1991), taking advantage of the fact that prolonged storage at different temperatures resulted in different weight average molar mass,  $M_w$ , facilitating the use of the “Mark-Houwink-Kuhn-Sakurada”- (MHKS) power law relation linking  $[\eta]$  with  $M_w$ :

$$[\eta] \propto M_w^a \quad (6)$$

The MHKS exponent ( $a$ ) is derived using double logarithmic plot of intrinsic viscosities versus molar mass (**Figure 2**). In this case we find a value for the exponent,  $a$ , of  $(0.95 \pm 0.01)$  which is indicative of a rigid rod type molecule and is in good agreement with previous estimates: 1.0 (Cölfen et al., 2001);  $0.96 \pm 0.10$  (Fee et al., 2003);  $0.90 \pm 0.20$  (Rinaudo, 2006) and  $0.87 \pm 0.18$  (Kasaai, 2007) the latter two being the average exponent for 6 and 14 different solvent conditions, respectively. This procedure assumes a homologous series for the polymers (*i.e.* they all have approximately the same conformation type): any departure would reveal itself as non-linearity of the logarithmic plots. The dominance of hydrodynamic interactions

between chain segments is taken to render insignificant any contribution to the value of the coefficient though solvent draining effects (Tanford, 1961).

<Figure 2 here>

## 2. The translational frictional ratio, $f/f_0$

The translational frictional ratio (Tanford, 1961),  $f/f_0$  is a parameter which depends on molar mass, conformation *and* molecular expansion through hydration effects. It can be measured experimentally from the sedimentation coefficient and molar mass:

$$\frac{f}{f_0} = \frac{M_w(1 - \bar{v}\rho_{20,w})}{(N_A 6\pi\eta_{20,w}s_{20,w}^0)} \left( \frac{4\pi N_A}{3\bar{v}M_w} \right)^{1/3} \quad (7)$$

Values in the range 11 – 16 (**Table 2**) are considerably greater than the theoretical minimum of 1 and could either be due to long chain elongation or a high degree of expansion through (aqueous) solvent association, or a combination of both.

## 3. Wales-van Holde ratio, $R = k_s/[\eta]$

Values for the Wales-van Holde ratio (Wales, & van Holde, 1954) in the range 0.39 - 0.73 (**Table 2**) are obtained which are similar to those found previously 0.26 – 0.73 (Cölfen et al., 2001) and are again consistent with extended structures (Morris, Foster, & Harding, 2000, Morris, García de al Torre, Ortega, Castile, Smith, & Harding, 2008) but short of the limit for rod (0.15) (Harding, Berth, Ball, Mitchell, & García de la Torre, 1991). It has been previously reported that chitosans of higher molar mass become more compact (Berth et al., 1998) although this is contradicted by the Cölfen et al (2001) data and also by the new data which both show a decrease in the Wales van Holde ratio with increase in molar mass, indicating the opposite.

## 4. Sedimentation Conformation Zoning

The sedimentation conformation zone (Pavlov, Rowe, & Harding, 1997; Pavlov, Harding, & Rowe, 1999) plot of  $\log [s]/M_L$  versus  $\log k_s M_L$  enables an estimate of the “overall” solution conformation of a macromolecule in solution ranging from Zone A

(extra rigid rod) to Zone E (globular or branched). The parameter  $[s]$  related to the sedimentation coefficient by the relation

$$[s] = \frac{s_{20,w}^0 \eta_{20,w}}{M_L (-\bar{v} \rho_{20,w})} \quad (8)$$

and  $M_L$  the mass per unit length  $\approx 420 \text{ g mol}^{-1} \text{ nm}^{-1}$  (Vold, 2004).

The sedimentation conformation zoning (**Figure 3** and **Table 2**) places all three chitosans as Zone B (rigid rod), although the chitosans 1 and 8 are very close to the boundary with Zone C (semi-flexible coils).

<Figure 3 and Table 2 here>

##### 5. Combined “Global” Analysis: Multi\_HYDFIT

The linear flexibility of polymer chains can also be represented in terms of the persistence length,  $L_p$  of equivalent *worm-like chains* (Kratky, & Porod, 1949) where the persistence length is defined as the average projection length along the initial direction of the polymer chain and for a theoretical perfect random coil  $L_p = 0$  and for the equivalent extra-rigid rod (Harding, 1997)  $L_p = \infty$ , although in practice limits of  $\sim 1 \text{ nm}$  for random coils (*e.g.* pullulan) and  $200 \text{ nm}$  for an extra-rigid rod (*e.g.* schizophyllan) are more appropriate (Tombs, & Harding, 1998).

The persistence length and mass per unit length can be estimated using the *Multi\_HYDFIT* program (Ortega, & García de la Torre, 2007), which considers data sets of intrinsic viscosities and sedimentation coefficients for different molar mass. It then performs a minimisation procedure finding the best values of  $M_L$  and  $L_p$  and chain diameter  $d$  satisfying the Bushin-Bohdanecky (Bohdanecky, 1983; Bushin, Tsvetkov, Lysenko, & Emel’yanov, 1981) and Yamakawa-Fujii (Yamakawa, & Fujii, 1973) equations (equations 9 & 10). Extensive simulations have shown that values returned for  $M_L$  and  $L_p$  are insensitive to  $d$ , so this is usually fixed (Ortega, & García de la Torre, 2007).

$$\left(\frac{M_w^2}{\Delta}\right)^{1/3} = A_0 M_L \Phi^{-1/3} + B_0 \Phi^{-1/3} \left(\frac{2L_p}{M_L}\right)^{-1/2} M_w^{1/2} \quad (9)$$

$$s^0 = \frac{M_L \bar{v} \rho_0}{3\pi\eta_0 N_A} \times \left[ 1.843 \left(\frac{M_w}{2M_L L_p}\right)^{1/2} + A_2 + A_3 \left(\frac{M_w}{2M_L L_p}\right)^{-1/2} + \dots \right] \quad (10)$$

$$d = \left(\frac{4M_L \bar{v}}{\pi N_A}\right)^{1/2} \quad (11)$$

where  $M_L \approx 420 \text{ g mol}^{-1} \text{ nm}^{-1}$  (Vold, 2004) and the partial specific volume,  $\bar{v} = 0.57 \text{ ml g}^{-1}$  (Errington et al., 1993) and therefore  $d \approx 0.7 \text{ nm}$ .

The Multi\_HYDFIT program then floats the variable parameters in order to find a minimum of the multi-sample target (error) function (Ortega, & García de la Torre, 2007),  $\Delta$ . In this procedure as defined in Ortega and García de la Torre (2007),  $\Delta$  is calculated using equivalent radii, where the equivalent radius ( $a_v$ ) is defined as the radius of an equivalent sphere having the same value as the determined property. In the present study, we are interested in the equivalent radii resulting from the sedimentation coefficient i.e. translational frictional coefficient ( $a_T$ ) and from the intrinsic viscosity ( $a_I$ ).

$$a_T = \frac{f}{6\pi\eta_0} \quad (12)$$

where  $\eta_0$  is the viscosity of water at 20.0 °C, and

$$a_I = \left(\frac{3[\eta]M_w}{10\pi N_A}\right)^{1/3} \quad (13)$$

where  $N_A$  is Avogadro's number.

The target function,  $\Delta$  can be evaluated from the following relations:

$$\Delta^2 = \frac{1}{N_s} \sum_{i=1}^{N_s} \left[ \left( \sum_T W_T \right)^{-1} \sum_T W_T \left( \frac{a_T^{cal} - a_T^{exp}}{a_T^{exp}} \right)^2 \right] \quad (14)$$

$$\Delta^2 = \frac{1}{N_s} \sum_{i=1}^{N_s} \left[ \left( \sum_I W_I \right)^{-1} \sum_I W_I \left( \frac{a_I^{cal} - a_I^{exp}}{a_I^{exp}} \right)^2 \right] \quad (15)$$

where  $N_s$  is the number of samples in multi-sample analysis,  $W_T$  and  $W_I$  are the statistical weights for equivalent radii  $a_T$  and  $a_I$  (from translation frictional coefficient and intrinsic viscosity data, respectively) and the subscripts cal and exp represent values from calculated and experimental values, respectively.

$\Delta$  is thus a dimensionless estimate of the agreement between the theoretical calculated values for the intrinsic viscosity for a particular molar mass, persistence length and mass per unit length and the experimentally measured parameters (Ortega, & García de la Torre, 2007), therefore the value of  $\Delta$  multiplied by 100 % is the percentage difference between theoretical and calculated values.

<Figure 4 here>

The minimum in the target function ( $\Delta = 0.09$ ) corresponds to a persistence length of  $(16 \pm 2)$  nm and a mass per unit length of  $(450 \pm 20)$  g mol<sup>-1</sup> nm<sup>-1</sup> (**Figure 4**). If we fix the mass per unit length to 420 nm (Vold, 2004), we find a persistence length of 14 nm. It should, however, be noted that all values of  $\Delta$  in the first contour vary by less than the experimental error  $\sim 2$  % and, therefore, we are most likely looking at a spectrum of probable conformations where  $L_p$  and  $M_L$  range from 5 – 40 nm and 220 – 650 g mol<sup>-1</sup> nm<sup>-1</sup>, respectively, which may go some way to explaining why chitosan has been described as either a semi-flexible coil or a rigid rod.

## Conclusions

Several previous studies on the solution conformation of chitosan (**Table 3**) (Terbojevich et al., 1991; Errington et al., 1993; Cölfen et al., 2001; Fee et al., 2003; Kasaai, 2007) have suggested a rigid rod conformation whilst others (Rinaudo et al., 1993; Berth et al., 1998; Brugnerotto et al., 2001; Schatz et al., 2003; Mazeau and Rinaudo, 2004; Vold, 2004; Larmarque et al., 2005; Velasquez et al., 2008) have adopted a semi-flexible coil model.

<**Table 3 here**>

This apparent discrepancy has been in part explained by the new Multi\_HYDFIT approach (Ortega, & Garcia de la Torre, 2007) which has shown that conformation of chitosan is close to the semi-flexible coil – rigid rod limit and that there are a large number of possible conformations which could fall in to either of these categories (**Figure 4**). This observation would not have been possible with the more traditional

Bushin-Bohdanecky analysis of plotting  $\left(\frac{M_w^2}{[\eta]}\right)^{1/3}$  versus  $M_w^{1/2}$  (**Figure 5**).

It may therefore be prudent to describe the solution conformation of chitosan as a semi-flexible rod (or stiff coil).

<**Figure 5 here**>

## References

Berth, G., Dautzenberg, H., & Peter, M. G. (1998). Physico-chemical characterization of chitosans varying in degree of acetylation. *Carbohydrate Polymers*, **36**, 205-216.

Bohdanecky, M. (1983). New method for estimating the parameters of the wormlike chain model from the intrinsic viscosity of stiff-chain polymers. *Macromolecules*, **16**, 1483-1493.

Brugnerotto J., Desbrières J., Roberts G., & Rinaudo M. (2001). Characterization of chitosan by steric exclusion chromatography. *Polymer*, **42**, 9921–9927.

Bushin, S. V., Tsvetkov, V. N., Lysenko, Y. B., & Emel'yanov, V. N. (1981). Conformational properties and rigidity of molecules of ladder polyphenylsiloxane in solutions according the data of sedimentation-diffusion analysis and viscometry. *Vysokomolekulyarnye Soedineniya*, **A23**, 2494-2503.

Cölfen H., Berth, G., & Dautzenberg, H. (2001). Hydrodynamic studies on chitosans in aqueous solution. *Carbohydrate Polymers*, **45**, 373-383.

Errington, N., Harding, S. E., Vårum, K. M., & Illum, L. (1993). Hydrodynamic characterisation of chitosans varying in degree of acetylation. *International Journal of Biological Macromolecules*, **15**, 113-117.

Fee, M., Errington, N., Jumel, K., Illum, L, Smith, A., & Harding, S. E. (2003). Correlation of SEC/MALLS with ultracentrifuge and viscometric data for chitosans. *European Biophysical Journal*, **32**, 457-464.

Gralén, N. (1944). *Sedimentation and diffusion measurements on cellulose and cellulose derivatives*. PhD Dissertation, University of Uppsala, Sweden.

Harding, S. E. (1997). The Intrinsic viscosity of biological macromolecules. Progress in measurement, interpretation and application to structure in dilute solution. *Progress in Biophysics and Molecular Biology*, **68**, 207-262.

Harding, S. E. (2005). Analysis of polysaccharides size, shape and interactions. In D. J. Scott, S. E. Harding, & A. J. Rowe (Eds.). *Analytical Ultracentrifugation Techniques and Methods* (pp. 231-252). Cambridge: Royal Society of Chemistry.

Harding, S. E., Davis, S. S. Deacon, M. P., & Fiebrig, I. (1999). Biopolymer mucoadhesives. In: Harding, S. E. (Ed.) *Biotechnology and Genetic Engineering Reviews Vol. 16*. Intercept: Andover, UK. Pages 41-86.

Harding, S. E., Vårum, K. M., Stokke, B. T., & Smidsrød, O. (1991). Molar mass determination of polysaccharides. In C. A. White (Ed.). *Advances in Carbohydrate Analysis Vol. 1*. JAI Press Limited: Greenwich, USA. Pages 63-144.

Harding, S. E.; Berth, G.; Ball, A.; Mitchell, J. R., & García de la Torre, J. (1991). The molar mass distribution and conformation of citrus pectins in solution studied by hydrodynamics. *Carbohydrate Polymers*, **168**, 1-15.

Kasaai, M. R. (2006). Calculation of Mark–Houwink–Sakurada (MHS) equation viscometric constants for chitosan in any solvent–temperature system using experimental reported viscometric constants data. *Carbohydrate Polymers*, **68**, 477-488.

Kratky, O., & Porod, G. (1949). Röntgenuntersuchung gelöster fadenmoleküle. *Recueil Des Travaux Chimiques Des Pays-Bas*, **68**, 1106-1109.

Lamarque, G., Lucas, J-M., Viton, C., & Domard, A. (2005). Physicochemical behavior of homogeneous series of acetylated chitosans in aqueous solution: role of various structural parameters. *Biomacromolecules*, **6**, 131-142.

Mazeau K., & Rinaudo M. (2004). The prediction of the characteristics of some polysaccharides from molecular modelling. Comparison with effective behaviour. *Food Hydrocolloids*, **18**, 885–898.

Morris, G. A.; Foster, T. J., & Harding, S. E. (2000). The effect of degree of esterification on the hydrodynamic properties of citrus pectin. *Food Hydrocolloids*, **14**, 227-235.

Morris, G. A., García de al Torre, J., Ortega, A., Castile, J., Smith, A., & Harding, S. E. (2008). Molecular flexibility of citrus pectins by combined sedimentation and viscosity analysis. *Food Hydrocolloids*, **22**, 1435-1442.

Ortega, A., & García de la Torre, J. (2007). Equivalent radii and ratios of radii from solution properties as indicators of macromolecular conformation, shape, and flexibility. *Biomacromolecules*, **8**, 2464-2475.

Pavlov, G. M.; Rowe, A. J., & Harding, S. E. (1997). Conformation zoning of large molecules using the analytical ultracentrifuge. *Trends in Analytical Chemistry*, **16**, 401-405.

Pavlov, G. M.; Harding, S. E., & Rowe, A. J. (1999). Normalized scaling relations as a natural classification of linear macromolecules according to size. *Progress in Colloid and Polymer Science*, **113**, 76-80.

Ralston, G. (1993). *Introduction to Analytical Ultracentrifugation* (pp 27-28). Palo Alto: Beckman Instruments Inc.

Rinaudo, M. (2006). Chitin and chitosan: properties and applications. *Progress in Polymer Science*, **31**, 603-632.

Rinaudo, M., Milas, M., & Le Dung, P. (1993). Characterization of chitosan. Influence of ionic strength and degree of acetylation on chain expansion. *International Journal of Biological Macromolecules*, **15**, 281-285.

Rowe, A. J. (1977). The concentration dependence of transport processes: a general description applicable to the sedimentation, translational diffusion and viscosity coefficients of macromolecular solutes. *Biopolymers*, **16**, 2595-2611.

Schatz, S. Viton, C., Delair, T. Pichot, C., & Domard, A. (2003). Typical physicochemical behaviors of chitosan in aqueous solution. *Biomacromolecules*, **4**, 641-648.

Schuck, P. (1998). Sedimentation analysis of noninteracting and self-associating solutes using numerical solutions to the Lamm equation. *Biophysical Journal*, **75**, 1503-1512.

Schuck, P. (2005). Diffusion-deconvoluted sedimentation coefficient distributions for the analysis of interacting and non-interacting protein mixtures. In D. J. Scott, S. E. Harding, & A. J. Rowe (Eds.). *Analytical Ultracentrifugation Techniques and Methods* (pp. 26-50). Cambridge: Royal Society of Chemistry.

Solomon, O. F., & Ciutâ, I. Z. (1962). Détermination de la viscosité intrinsèque de solutions de polymères par une simple détermination de la viscosité. *Journal of Applied Polymer Science*, **24**, 683-686.

Tanford, C. (1961). *Physical Chemistry of Macromolecules*. New York: John Wiley and Sons.

Terbojevich, M. Cosani, A., Conio, G., Marsano, E., & Bianchi, E. (1991). Chitosan: chain rigidity and mesophase formation. *Carbohydrate Research*, **209**, 251-260.

Tombs, M. P., & Harding, S. E. (1998). *Polysaccharide Biotechnology*. Taylor Francis: London, UK. Pages 144-151.

Velásquez, C. L., Albornoz, J. S., & Barrios, E. M. (2008). Viscosimetric studies of chitosan nitrate and chitosan chlorhydrate in acid free NaCl aqueous solution. *E-Polymers*, 014.

Vold, I. M. N. (2004). *Periodate Oxidised Chitosans: Structure and Solution Properties*. PhD Dissertation, Norwegian University of Science and Technology, Trondheim, Norway.

Wales, M., & van Holde, K. E. (1954). The concentration dependence of the sedimentation constants of flexible macromolecules. *Journal of Polymer Science*, **14**, 81-86.

Yamakawa, H., & Fujii, M. (1973). Translational friction coefficient of wormlike chains. *Macromolecules*, **6**, 407-415.

**Table 1** - solution properties for chitosan in 0.2 M pH 4.3 acetate buffer

Sample	$[\eta]$ (ml g <sup>-1</sup> )	$M_w$ (g mol <sup>-1</sup> )	Sample	$[\eta]$ (ml g <sup>-1</sup> )	$M_w$ (g mol <sup>-1</sup> )
<b>Chitosan-1</b>	1765 ± 55	425000 ± 20000	<b>Chitosan-18</b>	845 ± 25	205000 ± 20000
<b>Chitosan-2</b>	1350 ± 40	400000 ± 15000	<b>Chitosan-19</b>	815 ± 25	195000 ± 5000
<b>Chitosan-3</b>	1530 ± 45	380000 ± 20000	<b>Chitosan-20</b>	745 ± 20	175000 ± 5000
<b>Chitosan-4</b>	1370 ± 40	365000 ± 15000	<b>Chitosan-21</b>	655 ± 20	160000 ± 5000
<b>Chitosan-5</b>	1175 ± 35	340000 ± 5000	<b>Chitosan-22</b>	555 ± 15	130000 ± 5000
<b>Chitosan-6</b>	1210 ± 35	320000 ± 15000	<b>Chitosan-23</b>	440 ± 15	130000 ± 5000
<b>Chitosan-7</b>	1120 ± 35	320000 ± 10000	<b>Chitosan-24</b>	490 ± 15	115000 ± 5000
<b>Chitosan-8</b>	1450 ± 40	290000 ± 20000	<b>Chitosan-25</b>	465 ± 15	115000 ± 5000
<b>Chitosan-9</b>	1180 ± 35	290000 ± 20000	<b>Chitosan-26</b>	460 ± 15	115000 ± 5000
<b>Chitosan-10</b>	1075 ± 30	290000 ± 15000	<b>Chitosan-27</b>	430 ± 15	105000 ± 5000
<b>Chitosan-11</b>	1265 ± 40	275000 ± 20000	<b>Chitosan-28</b>	355 ± 10	105000 ± 5000
<b>Chitosan-12</b>	1125 ± 35	270000 ± 20000	<b>Chitosan-29</b>	415 ± 10	100000 ± 5000
<b>Chitosan-13</b>	1020 ± 30	270000 ± 20000	<b>Chitosan-30</b>	450 ± 15	95000 ± 5000
<b>Chitosan-14</b>	1185 ± 35	260000 ± 20000	<b>Chitosan-31</b>	345 ± 10	75000 ± 5000
<b>Chitosan-15</b>	925 ± 30	235000 ± 20000	<b>Chitosan-32</b>	320 ± 10	70000 ± 5000
<b>Chitosan-16</b>	960 ± 30	230000 ± 20000	<b>Chitosan-33</b>	270 ± 10	65000 ± 5000
<b>Chitosan-17</b>	825 ± 25	225000 ± 5000			


**Table 2** - Hydrodynamic parameters derived from sedimentation velocity

<b>Sample</b>	<b><math>s_{20,w}^0</math> (S)</b>	<b><math>k_s</math> (ml g<sup>-1</sup>)</b>	<b><math>k_s/[\eta]</math></b>	<b><math>f/f_0</math></b>	<b>Zone</b>
<b>Chitosan-1</b>	2.15 ± 0.18	680 ± 40	0.39 ± 0.05	16 ± 2	B/C
<b>Chitosan-8</b>	2.13 ± 0.13	800 ± 100	0.55 ± 0.10	13 ± 1	B/C
<b>Chitosan-25</b>	1.38 ± 0.07	340 ± 30	0.73 ± 0.05	11 ± 1	B


**Table 3** - Persistence length and mass per unit length estimates for chitosan

<b>Persistence length, <math>L_p</math> (nm)</b>	<b>Mass per unit length, <math>M_L</math> (g mol<sup>-1</sup> nm<sup>-1</sup>)</b>	<b>Reference</b>
16 ± 2	450 ± 20	This study
22 - 35	-	Terbojevich et al., 1991
6 - 13	340	Berth et al., 1998
5 - 13	350	Cölfen et al., 2001
11 - 15	-	Brugnerotto et al., 2001
4 - 6	-	Schatz et al., 2003
11 - 15	-	Mazeau and Rinaudo, 2004
5 - 9	350 - 470	Vold, 2004
6 - 15	-	Larmarque et al., 2005
8 - 17	-	Velasquez et al., 2008


## Figures

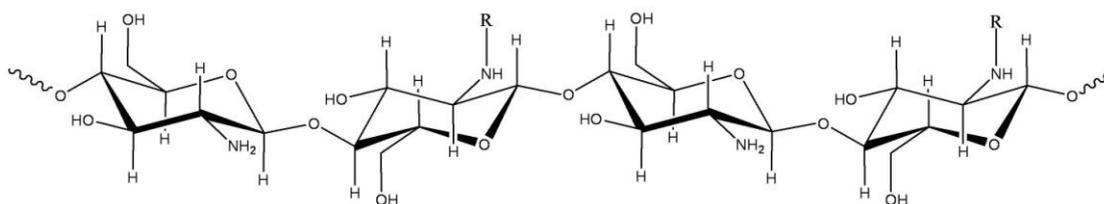


**Figure 1.** Schematic representation of the structure repeat units of chitosan, where R = Ac or H depending on the degree of acetylation.

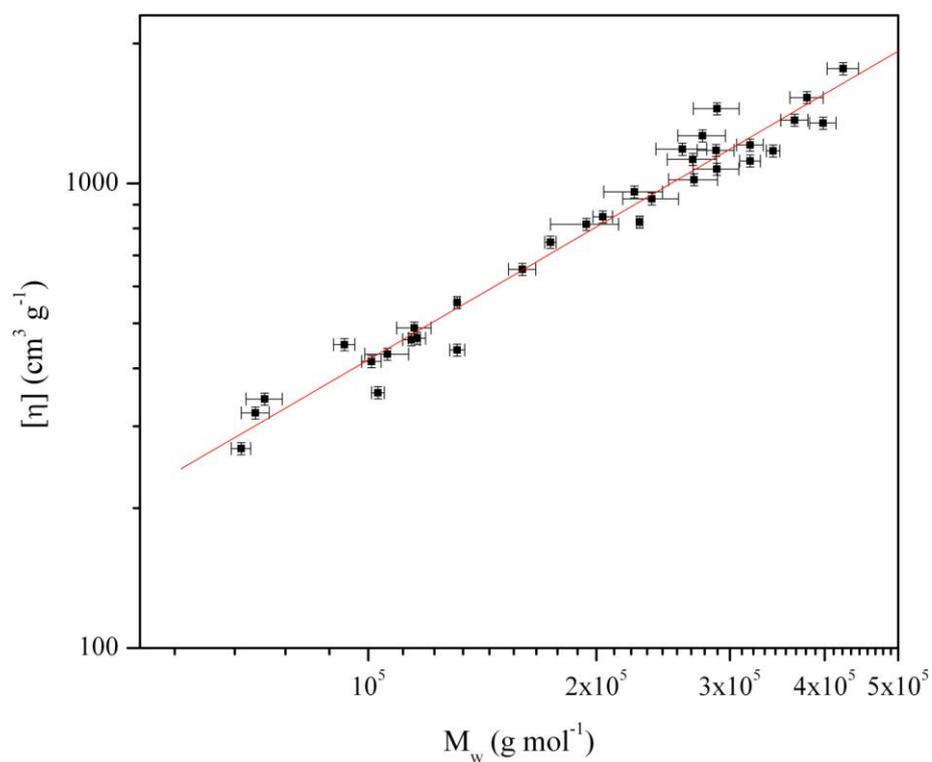


**Figure 2.** Mark-Houwink-Kuhn-Sakurada power law double logarithmic plot for chitosan where the slope,  $a = 0.95 \pm 0.01$ , the intercept  $\log k = -2.13 \pm 0.05$  and therefore  $k = 7.4 \pm 0.9 \times 10^{-3} \text{ ml g}^{-1}$ .

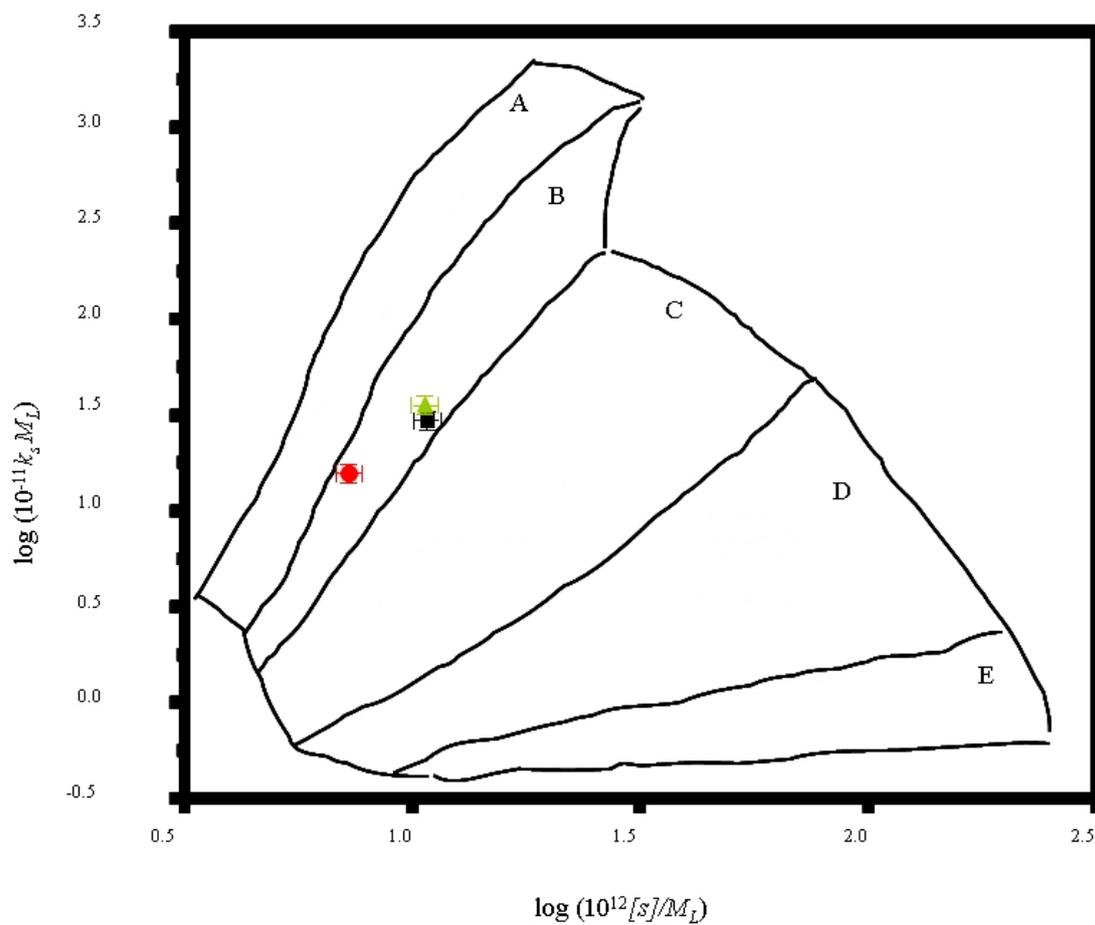

**Figure 3.** The sedimentation conformation zoning plot (adapted from Pavlov et al., 1997; Pavlov et al., 1999). Zone A: extra rigid rod; Zone B: rigid rod; Zone C: semi-flexible; Zone D: random coil and Zone E: globular or branched. Individual chitosans are marked: chitosan-1 (■); chitosan-8 (▲) and chitosan-25 (●).

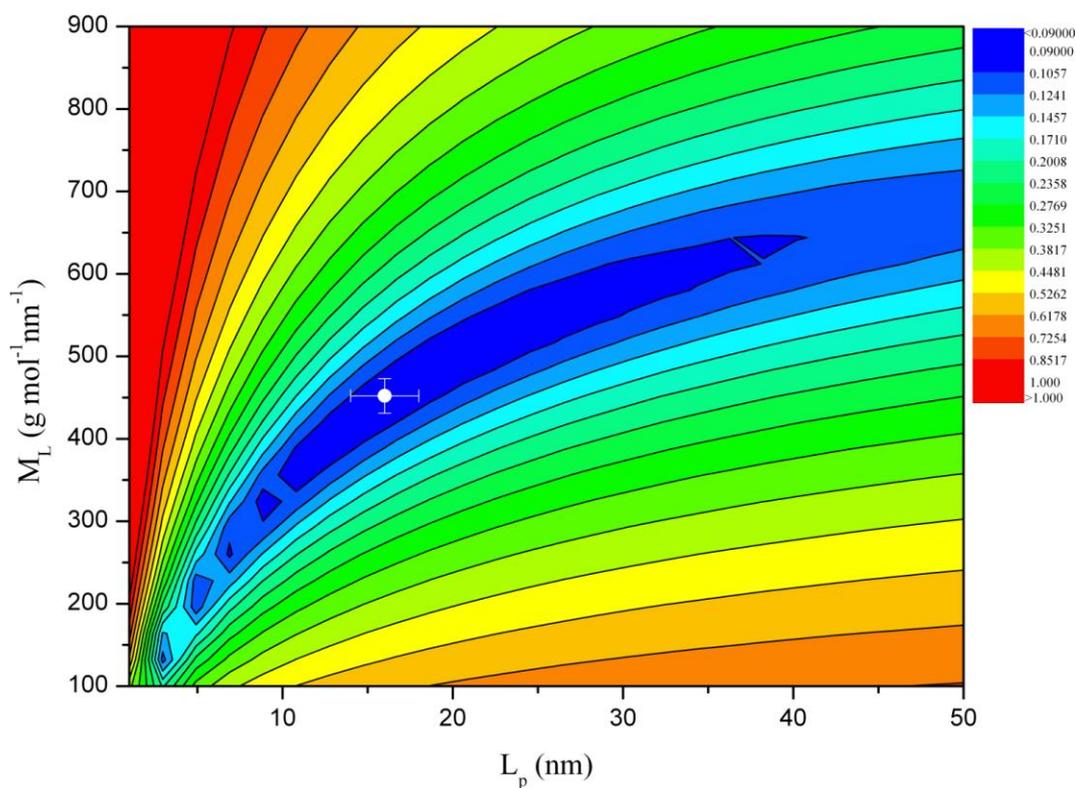

**Figure 4.** Solutions to the Bushin-Bohdanecky equations for chitosan using equivalent radii approach. The x-axis and y-axis represent  $L_p$  (nm) and  $M_L$  ( $\text{g mol}^{-1} \text{nm}^{-1}$ ), respectively. The target function,  $\Delta$  is calculated over a range of values for  $M_L$  and  $L_p$ . In these representations, the values of  $\Delta$  function are represented by the full colour spectrum, from the minimum in the target function in blue ( $\Delta = 0.09$ ) to red ( $\Delta \geq 1$ ). The calculated minimum ( $L_p = 16 \pm 2$  nm and  $M_L = 450 \pm 20$   $\text{g mol}^{-1} \text{nm}^{-1}$ ) is indicated.

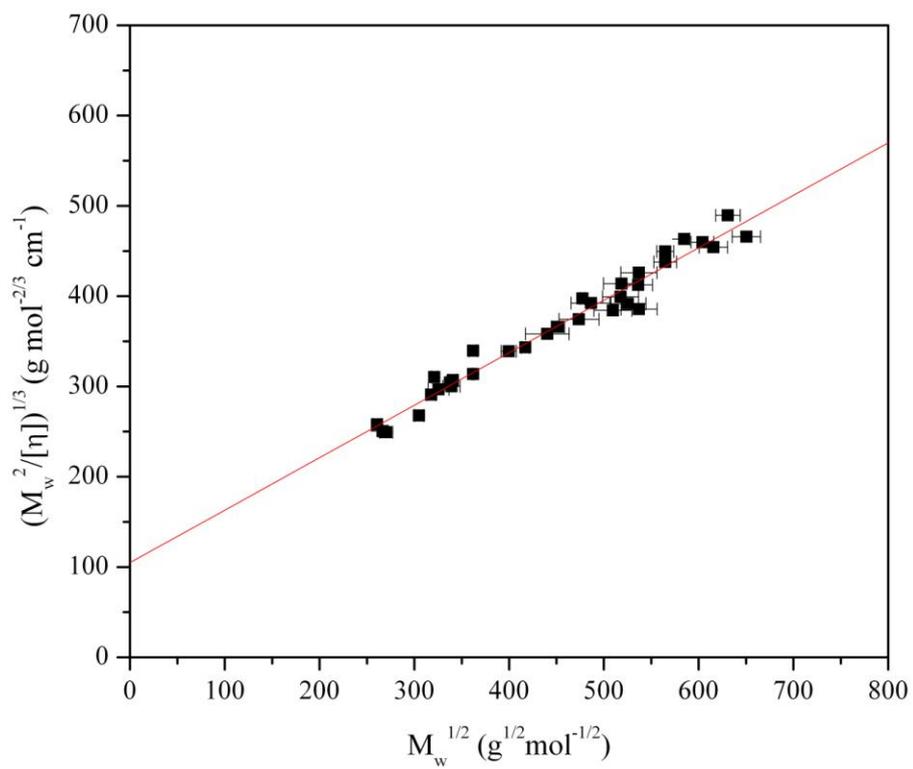

**Figure 5.** Bushin-Bohdanecky plot for chitosan where  $L_p = 22 \pm 2$  nm from the slope and  $M_L = 520 \pm 20$   $\text{g mol}^{-1}\text{nm}^{-1}$  from the intercept.